

Jan van Meerveld

A method to extract the monomer friction coefficient from the linear viscoelastic behavior of linear, entangled polymer melts

Received: 26 November 2003
Accepted: 15 January 2004
Published online: 20 March 2004
© Springer-Verlag 2004

J. van Meerveld
Institute of Polymers, Department of
Materials, ETH-Zürich, ETH-Zentrum,
Zürich, Switzerland
E-mail: meerveld@mat.ethz.ch

Abstract The rheological properties of isotactic and atactic polypropylene melts are analyzed in order to obtain the equilibration time, τ_e , and monomer friction coefficient, ζ . A procedure is proposed to determine τ_e from the zero shear rate viscosity, η_0 , using the magnitude of the molecular weight per entanglement, M_e , from the literature. This procedure can be applied to both mono- and polydisperse linear, entangled polymer melts. For different polymers this procedure gives very similar results compared to the description of the storage and loss modulus of nearly monodisperse linear, entangled polymer melts by molecular based theories, as well as

with values of ζ reported in the literature for linear, non-entangled polymer melts. It is observed that for isotactic and atactic polypropylene M_e differs by a factor 1.25 depending on the approach taken. As a consequence, the magnitude of τ_e and ζ differ by a factor of about 3.0 and 1.8, respectively. The knowledge of τ_e (or ζ) is of importance in order to obtain a better understanding of flow induced crystallization experiments on iPP.

Keywords Isotactic polypropylene · Atactic polypropylene · Linear polymer melts · Linear viscoelasticity · Monomer friction coefficient

Introduction

The rheological relevant time scales, as the reptation and longest Rouse time, can be directly related to the molecular weight (distribution) of the melt using molecular theories based on the tube concept (Doi and Edwards 1986). Alternatively, the rheological response influences the flow induced crystallization dynamics and consequently the semi-crystalline morphology of the material. In particular, the transition from the spherulitic to the so-called ‘shish-kebab’ morphology changes the solid-state properties of the material (Keller and Kolnaar 1997). The development of the shish-kebab morphology is generally believed to result from chain stretching of the high molecular weight, HMW, chains in the high end tail of the molecular weight distribution

of the melt (Vleeshouwers and Meijer 1996; Keller and Kolnaar 1997; Nogales et al. 2001; Seki et al. 2002). This implies that for the HMW chains the Deborah number based on the longest Rouse time, τ_R , $De_s = \tau_R \dot{\gamma}$ or $\tau_R \dot{\epsilon}$ is larger than 1, with $\dot{\gamma}$ and $\dot{\epsilon}$ the shear and extensional rate respectively. The magnitude of τ_R is related to the molecular weight, M , of the chains via (Doi and Edwards 1986; Larson et al. 2003)

$$\tau_R = \tau_e (M/M_e)^2. \quad (1)$$

The knowledge of M_e and the equilibration time τ_e (which is the Rouse relaxation time of a chain of length equal to one tube segment) is thus sufficient to determine τ_R directly from the molecular weight. (The magnitude of τ_e is directly related to the monomeric friction coefficient, ζ (Ferry 1980; Larson et al. 2003).) This

approach is advantageous as it is difficult, if not impossible, to obtain τ_R for the HMW chains experimentally from the linear viscoelastic regime (van Meerveld et al. 2003). In addition, it is likely that the stress contribution from the high-end tail is ‘screened’ by the remaining part of the MWD in shear flows (Graham et al. 2001). The drawback is that, to the best of my knowledge, τ_e or ζ is not reported in the literature for iPP, which is a popular material for flow induced crystallization experiments. This paper has the goal to obtain the magnitude of τ_e and ζ for iPP, as this is helpful to obtain a better understanding of the observations in flow induced crystallization experiments of iPP.

In the next section, two procedures are described to obtain τ_e from molecular based theories for linear, entangled polymer melts. In the following section these two procedures are evaluated for different polymer systems and the resulting magnitudes of ζ are compared with data reported in the literature, which are obtained for linear, non-entangled polymer melts. One procedure is applied to iPP and aPP in the section after that. Finally conclusions are drawn in the last section.

Theory

Definition of the molecular weight per entanglement from experiments

Before addressing the two procedures to obtain τ_e the different definitions of the molecular weight per entanglement, M_e , are introduced, where we follow the notation as used in Larson et al. (2003). The magnitude of M_e follows from the expression according to Ferry (1980):

$$M_e^F = \frac{\rho RT}{G_N^0} \quad (2)$$

or that proposed by Fetters et al. (1994):

$$M_e^G = \frac{4 \rho RT}{5 G_N^0}, \quad (3)$$

with R the universal gas constant, T the absolute temperature, ρ the density and G_N^0 the plateau modulus, which is accessible experimentally. For monodisperse melts the magnitude of G_N^0 can be determined by, first, integrating the area under the loss modulus vs frequency, G'' vs ω , plot (Ferry 1980), second, from creep experiments (Plazek and Plazek 1983), or third by using the phenomenological relationship, $G_N^0 = 3.56 G''_{\max}$ (Fetters et al. 1994, 1996, 1999).

Procedure A

The first procedure to determine τ_e is based on the fit of the storage modulus, $G'(\omega)$, and loss modulus, $G''(\omega)$, by

the molecular based model developed by Milner and McLeish (1998), the improved version by Likhtman and McLeish (2002), the LM-model, and the dual constraint model of Pattamaprom et al. (2000) and Pattamaprom and Larson (2001), the DC model. In this section only the relevant differences between the DC and LM model are discussed for the current purpose and the reader is referred to the original papers for the model formulations. The τ_e (or ζ) and M_e are the only adjustable parameters in both models. However, the DC model is based on M_e^F and the LM model on M_e^G . The difference between considering M_e^F and M_e^G affects, first, the number of entanglements, second, the numerical prefactor of τ_e and, third, the numerical prefactor of the time scale of ‘early time’ primitive path fluctuations, τ_{early} , as discussed in detail by Larson et al. (2003). The resulting differences between the LM and DC model are given in Table 1. (The significance of the tube length fluctuations changes in a non-linear fashion due to the combined effect of the differences on the time scales given in Table 1.) In addition two differences between the DC and LM model are of relevance. First, the ratio of the reptation time without tube length fluctuation, τ_d^0 , to the longest Rouse time, τ_R , is equal to $\tau_d^0/\tau_R = 3Z$ in the LM model, whereas in the DC model $\tau_d^0/\tau_R = 6Z$. Second, the description of the Rouse dynamics is different. In particular, the formulation of the Rouse dynamics in the LM model shows that 1/5 of the stress relaxes through ‘longitudinal relaxation modes’ in the terminal regime. The LM model thus naturally accounts for the numerical prefactor 4/5, which appears in the definition of M_e^G , Eq. (3). Consequently the modulus in the LM model is defined as $G^{\text{LM}} = \rho RT/M_e^G$, which is a factor 5/4 larger than the experimentally measured value of G_N^0 , i.e., $G^{\text{LM}} = 5G_N^0/4$. As a result of the differences in the DC and LM model the magnitude of τ_e is not identical

Table 1 Specification of the model parameters in the model of Likhtman and McLeish (2002) and the Dual-Constraint model (Pattamaprom et al. 2000): the molecular weight per entanglement, M_e , the modulus, G , the number of entanglements, Z , the equilibration time, τ_e , the time scale for ‘early time’ primitive path fluctuations, τ_{early} , and the ratio of the longest Rouse time, τ_R , to the reptation time without tube length fluctuations, τ_d^0 . It is noted that τ_{early} is not implemented in the LM model but resolved exactly by full chain simulations (Likhtman and McLeish 2002)

Model	Likhtman and McLeish	Dual-constraint
M_e	M_e^G	M_e^F
G	$\frac{\rho RT}{M_e^G}$	$\frac{\rho RT}{M_e^F}$
Z	M/M_e^G	M/M_e^F
τ_e	$\left(\frac{M_e^G}{M_0}\right)^2 \frac{\zeta b^2}{3\pi^2 k_b T}$	$\left(\frac{M_e^F}{M_0}\right)^2 \frac{\zeta b^2}{3\pi^2 k_b T}$
τ_{early}	$\frac{9}{16\pi^3} \tau_e Z^4 s^4$	$\frac{225}{256\pi^3} (\tau_e/2)(Z/2)^4 s^4$
τ_R	$\tau_e Z^2$	$\tau_e Z^2/2$
τ_d^0/τ_R	$3Z$	$6Z$

and therefore denoted as τ_e^{DC} and τ_e^{LM} respectively. From experiments it is observed that $2\tau_e^{\text{LM}} \approx \tau_e^{\text{DC}}$. In general it is possible to shift from the DC to the LM model by taking into account a correction factor of 5/4, or powers thereof, and using the experimentally observed relationship $2\tau_e^{\text{LM}} \approx \tau_e^{\text{DC}}$, see Table 2. The advantage of this procedure is that a good description of $G'(\omega)$ and $G''(\omega)$ in the terminal, the intermediate and the glassy regime requires a correct magnitude of both τ_e and M_e .

Procedure B

For different reasons $G'(\omega)$ and $G''(\omega)$ cannot be determined experimentally from the terminal to the glassy regime for melts of certain polymers. For example due to, first, the limited benefit from the time-temperature superposition principle (Kraft et al. 1999), second, a small temperature window due to a 'high' crystallization temperature and the onset of degradation at relative 'low' temperatures or, third, the difficulty to synthesize a melt of long monodisperse chains (Eckstein et al. 1998). In many cases only the terminal regime is accessible and the zero shear rate viscosity as a function of the weight averaged molecular weight, M_w , can be determined.

In procedure B M_e^G , or M_e^F , is taken from the literature (Fetters et al. 1994, 1996, 1999) and the magnitude of τ_e is determined from the zero shear rate viscosity, η_0 , as predicted by the DC and LM model. Actually, this approach is similar in spirit as reported by Ferry (1980). The important difference is that in the current approach the effect of tube length fluctuations is incorporated in the DC and LM model, which are essential to predict the scaling $\eta_0 \sim Z^{3.4}$.

Pattamaprom and Larson (2001) performed a mapping of the double reptation model (Tsenoglou 1987; des Cloizeaux 1988, 1990) on the predicted η_0 of the DC model. Doing so they arrive at the following expression between η_0 and τ_e :

$$\eta_0(M/M_e^F) = 0.051\tau_e^{\text{DC}}G_N^0(M/M_e^F)^{3.4}, \quad (4)$$

where M_e^F is used for consistency reasons. A similar exercise for the LM model, with the constraint release parameter c_v equal to one, $c_v=1.0$, (Likhtman and McLeish 2002) gives

$$\eta_0(M/M_e^G) = 0.064\tau_e^{\text{LM}}\frac{\rho RT}{M_e^G}(M/M_e^G)^{3.4}, \quad (5)$$

again using M_e^G to be consistent. It is noted that the numerical prefactor in Eq. (5), and consequently the magnitude of τ_e resulting from Eq. (5), depends on the magnitude of c_v .

For many polymers the η_0 as a function of M_w is available, which is represented by the phenomenological expression of the form

$$\eta_0(M_w) = \alpha M_w^\beta, \quad (6)$$

where the magnitude of α and β are given in Table 3, which is observed to hold for both mono- and polydisperse melts (Struglinski and Graessley 1985; Berger and Meissner 1992; Aguliar et al. 2003; Vega et al. 2003) in agreement with predictions of the DC model (Pattamaprom and Larson 2001). Observation of Table 3 illustrates that in a number of studies the exponent β equals the theoretical value of 3.4, but sometimes $\beta \approx 3.6$. It should be noted that for $\beta \approx 3.6$ the magnitude of α is roughly an order of magnitude smaller compared to $\beta=3.4$ for both PE and aPP. In the next two sections only the expressions with $\beta=3.4$ are used, which are consistent with Eqs. (4) and (5).

Application of procedure A and B, and comparison with data in the literature

In this section the magnitude of τ_e and ζ are determined for polyethylene, PE, hydrogenated polybutadiene,

Table 2 The magnitude of the modulus G , the molecular weight per entanglement, M_e , and the equilibration time, τ_e , for different polymers following from the different procedures. The magnitudes for A-LM are reported in Likhtman and McLeish (2002), or ob-

tained in the section 'Application of procedure A and B, and comparison with data in the literature', and for A-DC reported in Pattamaprom et al. (2000) and Pattamaprom and Larson (2001). n/a denotes not available

	Unit	Procedure	PE	PI	h-PBD	1,4-PBD	aPP	PS
T	K		463	298	463	301	348	442.5
G	kPa	A-LM	3250	536	2888	1840	757	269
M_e	g/mol	A-LM	860	4160	1000	1930	3150	14470
τ_e	s	A-LM	n/a	3.0×10^{-5}	3.5×10^{-9}	4.9×10^{-7}	5.7×10^{-6}	9.22×10^{-4}
τ_e	s	B-LM	1.45×10^{-9}	n/a	2.87×10^{-9}	4.56×10^{-7}	5.3×10^{-6}	8.21×10^{-4}
G	[kPa]	A-DC	2600	434	2310	1250	n/a	200
M_e	g/mol	A-DC	1035	5200	1250	2268	n/a	16625
τ_e	s	A-DC	7.0×10^{-9}	6.0×10^{-5}	7.0×10^{-9}	1.51×10^{-6}	n/a	1.96×10^{-3}
τ_e	s	B-DC	4.429×10^{-9}	n/a	9.23×10^{-9}	1.46×10^{-6}	n/a	2.15×10^{-3}

Table 3 Reported values of the parameters α and β in the expression $\eta_0 = \alpha M_w^\beta$ for different polymers at a temperature T

Material	Reference Units	$\alpha \times 10^{-15}$ Ns mol $^\beta$ /g $^\beta$	β -	T K
PE	Pearson et al. (1987)	3.76	3.64	448
PE	Wood-Adams et al. (2000)	3.40	3.6	463
PE	Aguilar et al. (2001)	31.7	3.41	463
h-PBD	Pattamaprom and Larson (2001)	30	3.41	463
1,4-PBD	Struglinksi and Graessley (1985)	363	3.41	298
aPP	Aguilar et al. (2003)	340	3.40	348
aPP	Pearson et al. (1988)	53.4	3.59	348
iPP	Wasserman and Graessley (1996)	5.32	3.60	463
PS	Wasserman and Graessley (1992)	16800	3.4	423
PS	Graessley and Roovers (1979)	97.7	3.41	442.5
PIB	Fetters et al. (1991)	4690	3.43	298

h-PBD, 1,4-polybutadiene, 1,4-PBD, atactic polypropylene, aPP, polyisoprene, PI, and polyisobutylene, PIB, and polystyrene, PS, using procedure A in the first subsection, and procedure B in the second subsection. In the third subsection the magnitude of ζ following from procedures A and B are compared with values reported in the literature for linear, non-entangled polymer melts.

Procedure A for the DC and LM model

The DC model has been compared to experimental results of mono- and polydisperse PS, h-PBD, 1,4-PBD, PI and PE melts in Pattamaprom et al. (2000) and Pattamaprom and Larson (2001), whereas the LM model is only compared to experiments on nearly monodisperse PS and 1,4-PBD in Likhtman and McLeish (2002). In order to perform the analysis for a larger number of polymer systems the LM model, with $c_v = 1$, is used to describe $G'(\omega)$ and $G''(\omega)$ of the nearly monodisperse h-PBD (Raju et al. 1979), PI (Fetters et al. 1993), and aPP (Pearson et al. 1988). Good agreement between the predictions of the LM model and the experimental results for PI (Fetters et al. 1993) and h-PBD (Raju et al. 1979) are obtained using $\tau_e^{\text{LM}} = 0.5\tau_e^{\text{DC}}$ and taking M_e^G from the literature; see Figs. 1 and 2 and Table 2. (In contrast to PS, PI, and h-PBD one observes that for 1,4-PBD $3\tau_e^{\text{LM}} \approx \tau_e^{\text{DC}}$. It should be noted that the magnitudes of G^{LM} and M_e^G of the LM model are adjusted independently in order to optimize the description of the 1,4-PBD melt, which is discussed in detail by Likhtman and McLeish (2002).) For $\rho = 825 \text{ kg/m}^3$ (Fetters et al. 1994), $M_e^G = 3150 \text{ g/mol}$ and $\tau_e = 5.7 \times 10^{-6} \text{ s}$ the linear viscoelastic response of aPP at $T = 348 \text{ K}$ (Pearson et al. 1988) is correctly predicted by the LM model; see Fig. 3. However, the magnitude of M_e^G is about a factor 1.25 smaller compared to $M_e^G = 4000 \text{ g/mol}$, which is obtained after a linear interpolation between the magnitudes reported at $T = 298 \text{ K}$ and $T = 413 \text{ K}$ in Fetters et al. (1994, 1996). For $M_e^G = 3150 \text{ g/mol}$ one obtains $G^{\text{LM}} = 757 \text{ kPa}$, which corresponds to $G_N^0 = 606 \text{ kPa}$. (The magnitude of G_N^0 deviates considerably from the

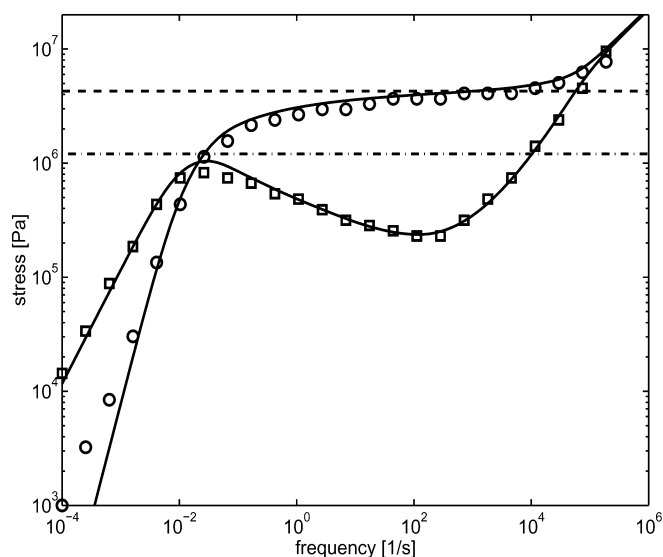


Fig. 1 The linear viscoelastic response of nearly monodisperse polyisoprenes, PI, at $T = 298 \text{ K}$. Predictions of the LM model (*full lines*). Experimental data are taken from Fetters et al. (1993). The *dashed line* indicates $4G^{\text{LM}}/5$ and the *dash-dotted line* the magnitude of G''_{max} according to $3.56G''_{\text{max}} = 4G^{\text{LM}}/5$

scattering in Figs. 1 and 2 of Fetters et al. (1994).) The chain characteristics and M_e^G of deuterated head-to-head polypropylene, dhhPP, are nearly identical to that of aPP (Fetters et al. 1994, 1999; Krishnamoorti et al. 2002). Therefore the description of $G'(\omega)$ and $G''(\omega)$ of the dhhPP melt at $T = 323 \text{ K}$ reported by Gell et al. (1997) is also fitted by the LM model to investigate if the deviation observed for the aPP melts is also found for the dhhPP melt. For $\rho = 922 \text{ kg/m}^3$ (Gell et al. 1997), $M_e^G = 2600 \text{ g/mol}$ and $\tau_e = 2.6 \times 10^{-4} \text{ s}$ the LM model correctly describes $G'(\omega)$ and $G''(\omega)$; see Fig. 4. Similar to the aPP melts, a good description of $G'(\omega)$ and $G''(\omega)$ of the dhhPP melt by the LM model requires one to take M_e^G smaller compared to the experimental value of $M_e^G = 4360 \text{ g/mol}$. In the case of dhhPP the difference is a factor 1.67. (The magnitude of M_e^G is the average of the three dhhPP melts investigated by Gell et al. (1997),

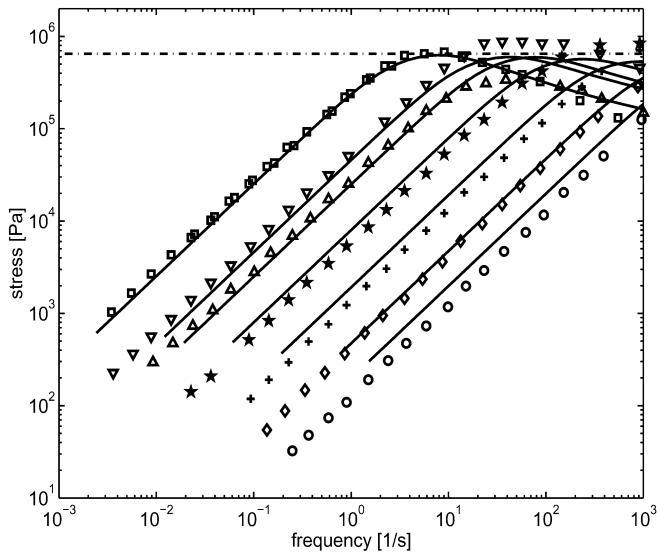


Fig. 2 The linear viscoelastic response of nearly monodisperse hydrogenated polybutadienes, h-PBD, at $T=463$ K. Predictions of the LM model (*full lines*). Experimental data are taken from Raju et al. (1979) for $M_w=41.7$ kg/mol (*open circles*), $M_w=53.3$ kg/mol (*open diamonds*), $M_w=80.3$ kg/mol (*crosses*), $M_w=123$ kg/mol (*stars*), $M_w=174$ kg/mol (*open triangles*), $M_w=211$ kg/mol (*inverted open triangles*), $M_w=360$ kg/mol (*open squares*). The dash-dotted line denotes the magnitude of G''_{\max} according to $3.56G''_{\max} = 4G^{\text{LM}}/5$

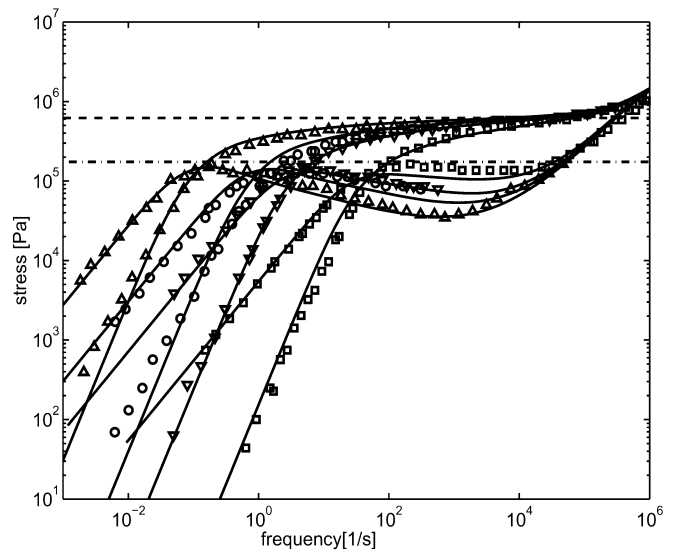


Fig. 3 The linear viscoelastic response of nearly monodisperse atactic polypropylene, aPP, at $T=348$ K. Predictions of the LM model (*full lines*). Experimental data are taken from Pearson et al. (1988) for $M_w=63.5$ kg/mol (*open squares*), $M_w=126$ kg/mol (*inverted open triangles*), $M_w=189$ kg/mol (*open circles*), $M_w=371$ kg/mol (*open triangles*). The dashed line indicates $4G^{\text{LM}}/5$ and the dash-dotted line the magnitude of G''_{\max} according to $3.56G''_{\max} = 4G^{\text{LM}}/5$

which follow from Eq. (3) using the reported values for G_N^0 and ρ by Gell et al. (1997).) It should be noted that for the aPP samples and dhhPP sample $G_N^0 J_e^0 \geq 4$ (Pearson et al. 1988; Gell et al. 1997) whereas $G_N^0 J_e^0$ is in general observed to be around 2.0–2.2 for monodisperse samples (Raju et al. 1981). This is believed to originate from a high molecular weight tail in the molecular weight distribution (Pearson et al. 1988; Gell et al. 1997).

Procedure B for the DC and LM model

For the application of procedure B the experimental relationship for $\eta_0(M_w)$ is taken from experiments on polydisperse melts. This is opposite to procedure A which can only be applied to monodisperse systems, at least for the LM model. To be consistent identical magnitudes of M_e^F and M_e^G are taken to determine τ_e^{DC} and τ_e^{LM} from Eqs. (4) and (5) respectively. The resulting magnitudes of τ_e^{DC} and τ_e^{LM} are given in Table 2. In general the magnitudes of τ_e^{DC} and τ_e^{LM} of procedures A and B differ by less than a factor 1.35, except for PE where a factor of 2 difference is observed. The good agreement is partly expected as the description of $G'(\omega)$ and $G''(\omega)$ in the terminal region, where $G'(\omega) \sim \omega^{-2}$ and $G''(\omega) \sim \omega^{-1}$, by the DC and LM model is closely related to the predicted η_0 .

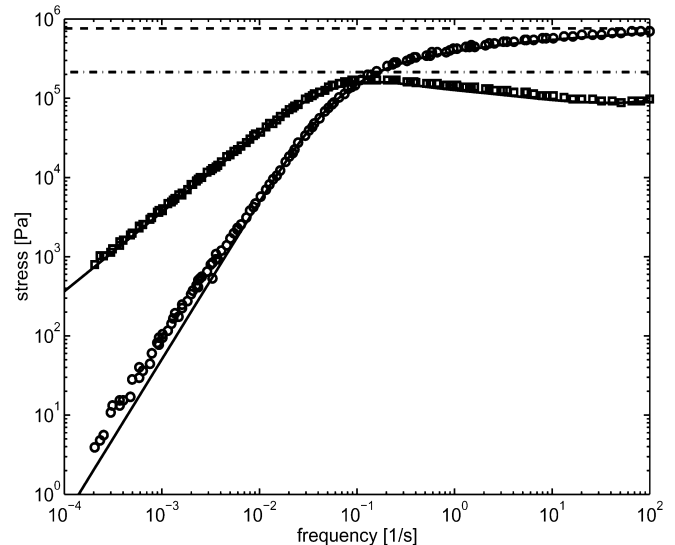


Fig. 4 The linear viscoelastic response of nearly monodisperse deuterated head-to-head polypropylene, dhhPP, at $T=323$ K. Predictions of the LM model (*full lines*). Experimental data (*symbols*) are taken from Gell et al. (1997). The dashed line indicates $4G^{\text{LM}}/5$ and the dash-dotted line the magnitude of G''_{\max} according to $3.56G''_{\max} = 4G^{\text{LM}}/5$

Comparison with other methods

Finally, the magnitude of ζ , which is directly related to τ_e , is compared with values of ζ reported in the

Table 4 Magnitude of the monomer friction coefficient ζ for different polymers obtained from procedure A of the LM model, A-LM, procedure B of the LM model, B-LM, using Eq. 7. Magnitudes of $\langle R^2 \rangle_0/M$ are taken from Fetters et al. (1994, 1996, 1999)

Material	T K	ζ : A-LM Ns/m	ζ : B-LM Ns/m	ζ : literature Ns/m	$\langle R^2 \rangle_0/M$ $\text{\AA}^2\text{mol/g}$
PE	463	n/a	4.15×10^{-13}	4.74×10^{-13a}	1.25
PI	298	4.13×10^{-10}	n/a	3.26×10^{-10b}	0.596
PIB	298	n/a	3.85×10^{-8}	4.47×10^{-8c}	0.570
PS	442.5	2.24×10^{-8}	1.56×10^{-8}	3.02×10^{-8d}	0.437
1,4-PBD	298	1.12×10^{-10}	9.95×10^{-11}	1.77×10^{-10e}	0.876

^aPearson et al. 1987^bExtracted from Fig. 2 of Haley et al. (2003)^cTable 12-II of Ferry (1980)^dMajeste et al. (1998); Pattamaprom et al. (2000)^eTable 12-II of Ferry (1980) for rubbers

literature. If possible, the magnitude of ζ is taken from measurements of the self-diffusion coefficient or viscosity of linear, non-entangled polymer melts, which are correctly described by the Rouse model. Contrary to linear, entangled polymer melts the influence of tube length fluctuations, tube dilation and constraint release are not of importance for linear, non-entangled polymer melts.

The τ_e and ζ are related to each other via the relationship (Larson et al. 2003)

$$\tau_e = \left(\frac{M_e^G}{M_0} \right)^2 \frac{\zeta b^2}{3\pi^2 k_B T} = \left(\frac{M_e^G}{M_0} \right) \frac{\zeta M_e^G [\langle R^2 \rangle_0/M]}{3\pi^2 k_B T}, \quad (7)$$

with M_0 the monomer molecular weight, b the monomer based segment length and $\langle R^2 \rangle_0$ the unperturbed mean square end-to-end distance. The magnitude of ζ , following from τ_e^{LM} , using procedure A and B of the LM model are given in Table 4. For polyisobutylene, PIB, the magnitude of τ_e^{LM} at $T=298$ K is obtained from procedure B of the LM model and using the expression for $\eta_0(M_w)$ reported by Fetters et al. (1991). Taking $G_N^0 = 330$ kPa and $M_e^G = 5700$ g/mol (Fetters et al. 1994) this gives $\tau_e^{\text{LM}} = 1.05 \times 10^{-3}$ s at $T=298$ K. Observation of Table 4 reveals that the magnitude of ζ following from procedure A and B of the LM model are in agreement with the values reported in the literature. Hence, this demonstrates that a good estimate of τ_e , or ζ , can be obtained using procedure A, or B, of the LM model.

Determination of the equilibration time and monomer friction coefficient for isotactic and atactic polypropylene

In the previous section it is shown that, for different polymer systems, procedure B of the LM model is suitable to obtain the magnitude of τ_e , or ζ . Therefore this procedure can be applied to determine τ_e for iPP. Procedure A cannot be followed due to the small temperature window between the temperature of crystallization and degradation in combination with the

Table 5 The magnitude of the plateau modulus G_N^0 , the molecular weight per entanglement, M_e^G , at a given absolute temperature T , reported in the literature for polydisperse aPP and iPP melts

Material	T [K]	G_N^0 [kPa]	M_e^G [g/mol]	Reference
aPP	296	452	3720	Plazek and Plazek (1983)
aPP	463	480–600	3900–4905	Vega et al. (2003)
aPP	463	410	5640	Eckstein et al. (1998)
iPP	463	430	5500	Eckstein et al. (1998)

difficulties to synthesize a melt of long nearly monodisperse iPP chains (Eckstein et al. 1998). In order to determine τ_e the magnitude of M_e^G , or G_N^0 , is required, which can be obtained in three different ways.

First, the plateau modulus, G_N^0 , is determined experimentally and M_e^G follows from Eq. (3). For monodisperse aPP melts at $T=348$ K, $G_N^0=480$ kPa and $M_e^G=4000$ g/mol, which follow from a linear interpolation between the reported experimental values at $T=298$ K and $T=413$ K in Fetters et al. (1994). For monodisperse iPP no data are reported. The magnitudes of G_N^0 and M_e^G reported in the literature for polydisperse aPP and iPP melts are given in Table 5. For aPP these values are in agreement with those of monodisperse aPP melts.

Second, the magnitude of G_N^0 and M_e^G can be determined from the relationships derived by Fetters et al. (1994, 1996, 1999), based on the concept of the packing length, p . The expressions for p and M_e^G are (Fetters et al. 1994)

$$p = \frac{M}{\langle R^2 \rangle_0 \rho N_A}, \quad (8)$$

$$M_e^G = B^2 \rho N_A p^3, \quad (9)$$

with B a temperature dependent constant, which equals 0.0516 at $T=413$ K and 0.0565 at $T=298$ K (Fetters et al. 1994). G_N^0 subsequently follows from Eq. (3). (For further details the reader is referred to the original paper.) It should be noted that the magnitude of M_e^G , following from Eq. (9), is in good agreement with the

Table 6 The magnitude of the plateau modulus G_N^0 , the molecular weight per entanglement, M_e^G , the equilibration time, τ_e , and the monomeric friction coefficient, ζ , for iPP and aPP based on procedure B of the model of Likhtman and McLeish (2002), LM. The

magnitude of $\langle R^2 \rangle_0/M$ is taken from Fetters et al. (1994) and Zirkel et al. (1992) for aPP and from Fetters et al. (1999) and Zirkel et al. (1992) for iPP

Material Units	T K	M_e^G g/mol	G_N^0 kPa	τ_e s	ζ Ns/m	$\langle R^2 \rangle_0/M$ $\text{\AA}^2\text{mol/g}$	
aPP	348	4000	470	1.60×10^{-5}	4.51×10^{-10}	0.664	Fetters et al. (1994)
aPP	348	3150	606	5.50×10^{-6}	2.51×10^{-10}	0.664	LM
iPP	463	5500	430	9.87×10^{-8}	1.86×10^{-12}	0.694	Fetters et al. (1999)
iPP	463	4400	538	3.54×10^{-8}	1.04×10^{-12}	0.694	LM

experimental value for monodisperse melts of many different polymers (Fetters et al. 1994, 1996, 1999). For iPP and aPP melts the density and the magnitude of $\langle R^2 \rangle_0/M$, as determined by SANS measurement of iPP and aPP chains in the melt, are nearly identical (Zirkel et al. 1992; Schweizer et al. 1995; Eckstein et al. 1998; Fetters et al. 1999; Krishamoorti et al. 2002). As the parameters in Eqs. (8) and (9) are nearly identical for iPP and aPP melts, this equally holds for M_e^G . The approximately identical values of iPP and aPP is confirmed by experiments (Eckstein et al. 1998), see Table 5, which are in good agreement with the predicted value from Eq. (9) (see Table 2 of Fetters et al. 1999).

Third, one may obtain a magnitude of M_e^G from the description of $G'(\omega)$ and $G''(\omega)$ by procedure A of the LM model. For PI, PS and h-PBD the magnitude of M_e^G based on this approach is identical to the experimental values for monodisperse melts, which are in good agreement with the predictions from Eq. (9). However, for nearly monodisperse aPP melts at $T=348$ K a good description of $G'(\omega)$ and $G''(\omega)$ (Pearson et al. 1988) by the LM model is obtained provided $M_e^G=3150$ g/mol. This magnitude is a factor 1.25 smaller compared to the experimental value for monodisperse aPP melts, $M_e^G=4000$ g/mol, reported by Fetters et al. (1994, 1996).

The variation in the magnitude of M_e^G is unsatisfactory because η_0 scales with M_e^G as $\eta_0 \sim \tau_e^{\text{LM}} G_N^0 (M/M_e^G)^{3.4} \sim \tau_e^{\text{LM}} M_e^{G-4.4}$, and consequently $\tau_e^{\text{LM}} \sim \eta_0 M_e^{G4.4}$. Hence, a small variation in M_e^G can have a strong effect on the estimated magnitude of τ_e^{LM} . Therefore two values of M_e^G and $G_N^0 (=4G^{\text{LM}}/5)$ are considered for the iPP and aPP melts in the remaining of this section.

For aPP at $T=348$ K the first set are the experimental values for the monodisperse melts reported by Fetters et al. (1994, 1996), $G_N^0=470$ kPa and $M_e^G=4000$ g/mol, and the second set are those following from the description of $G'(\omega)$ and $G''(\omega)$ by the LM model, $G_N^0=606$ kPa and $M_e^G=3150$ g/mol. Application of procedure B of the LM model gives $\tau_e^{\text{LM}}=1.60 \times 10^{-5}$ s for $M_e^G=4000$ g/mol and $\tau_e^{\text{LM}}=5.50 \times 10^{-6}$ s for $M_e^G=3150$ g/mol, respectively. Using Eq. (7) one obtains $\zeta=4.51 \times 10^{-10}$ s for $M_e^G=4000$ g/mol and $\zeta=2.51 \times 10^{-10}$ s for $M_e^G=3150$ g/mol, respectively.

For iPP at $T=463$ K the reported experimental values equal $G_N^0=430$ kPa and $M_e^G=5500$ g/mol (Eckstein et al. 1998; Fetters et al. 1999). Maintaining a ratio of 1.25 between the experimental value and that following from the LM model, as observed for aPP, the second parameter set is equal to $G_N^0=538$ kPa and $M_e^G=4400$ g/mol. For iPP at $T=463$ K this gives $\tau_e^{\text{LM}}=9.87 \times 10^{-8}$ s for $M_e^G=5500$ g/mol and $\tau_e^{\text{LM}}=3.54 \times 10^{-8}$ s for $M_e^G=4400$ g/mol, respectively. The magnitudes of ζ for iPP at $T=463$ K are equal to $\zeta=1.86 \times 10^{-12}$ s for $M_e^G=5500$ g/mol and $\zeta=1.04 \times 10^{-12}$ s for $M_e^G=4400$ g/mol, respectively. For aPP and iPP the magnitude of τ_e and ζ following from the different sets of M_e^G and G_N^0 are summarized in Table 6. It should be noted that the difference in ζ is smaller compared to τ_e^{LM} as $\tau_e^{\text{LM}} \sim \eta_0 M_e^{G4.4}$ whereas $\zeta \sim \eta_0 M_e^{G2.4}$. Hence, the variation of M_e^G by a factor of 1.25 results into a difference of about a factor 2.9 for τ_e^{LM} and about a factor 1.8 for ζ , respectively.

Conclusion

A procedure to estimate the equilibration time, τ_e , and the monomer friction coefficient, ζ , from the zero shear rate viscosity, η_0 , of linear, entangled polymer melts is given using the molecular weight per entanglement reported in the literature. For PE, h-PBD, 1,4-PBD, PS and aPP this gives an estimate of τ_e which is in good agreement with that obtained from the description of $G'(\omega)$ and $G''(\omega)$ using the molecular based model of Likhtman and McLeish (2002). The magnitude for ζ is also in good agreement with values reported in the literature for linear, non-entangled polymer melts of PE, PS, PIB and PI and that for a rubber of 1,4-PBD.

For aPP and dhhPP $G'(\omega)$ and $G''(\omega)$ are correctly predicted by the LM model provided the molecular weight per entanglement, M_e^G , is reduced by a factor 1.25 and 1.67, respectively, compared to the experimental value reported in the literature. Experimental results and the predicted magnitude of M_e^G , based on the concept of the packing length (Eq. 9), are in good agreement with

each other, and moreover indicate that the magnitude of M_e^G is approximately identical for aPP and iPP. Hence the question arises if one relies stronger on the experimental magnitude of M_e^G reported in the literature (Fetters et al. 1994, 1996, 1999) or that following from the description of $G'(\omega)$ and $G''(\omega)$ using the model of Likhtman and McLeish (2002). Finally, this difference in M_e^G results into a difference of about a factor 2.9 in the magnitude of τ_e and about a factor 1.8 in ζ respectively; see Table 6. The discrepancy in the magnitude of M_e^G may be resolved by an analysis of $G'(\omega)$ and $G''(\omega)$ using the LM model for a nearly monodisperse iPP or aPP melt where the magnitude of $G_N^0 J_e^0$ has the usual value in the range 2.0–2.2.

In view of the goal to obtain a better understanding of flow induced crystallization experiments on iPP only the longest Rouse time of the high molecular weight chains, $\tau_R = \tau_e (M/M_e^G)^2 \sim \zeta M^2$, is of interest. Here, one can partly benefit from the fact that a smaller M_e^G is balanced by a smaller τ_e . Finally, the difference in τ_R is about a factor 1.8, which is acceptable for the purpose to obtain an estimate of the Deborah numbers for chain stretching the high molecular weight chains.

Acknowledgement The author thanks Prof. Hans Christian Öttinger for helpful discussions and comments on the manuscript.

References

- Aguilar M, Vega JF, Sanz E, Marínez-Salazar J (2001) New aspects on the rheological behavior of metallocene catalyzed polyethylenes. *Polymer* 42:9713–9721
- Aguilar M, Vega JF, Pena B, Marínez-Salazar J (2003) Novel features of the rheological behavior of metallocene catalyzed atactic polypropylene. *Polymer* 44:1401–1407
- Berger L, Meissner J (1992) Linear viscoelasticity, simple and planar melt extension of linear polybutadienes with bimodal molar mass distributions. *Rheol Acta* 31:63–74
- des Cloizeaux J (1988) Double reptation vs simple reptation in polymer melts. *Europhys Lett* 5:437–442
- des Cloizeaux J (1990) Relaxation of entangled polymers in melts. *Macromolecules* 23:3392–4406
- Doi M, Edwards SF (1986) *The theory of polymer dynamics*. Clarendon Press, Oxford
- Eckstein A, Suhm J, Friedrich C, Maier R-D, Sassmannshausen J, Bochmann M, Mühlhaupt R (1998) Determination of plateau moduli and entanglement molecular weights of isotactic, syndiotactic and atactic polypropylenes synthesized with metallocene catalysts. *Macromolecules* 31:1335–1340
- Ferry JD (1980) *Viscoelastic properties of polymers*. Wiley, New York
- Fetters LJ, Graessley WW, Kiss AD (1991) Viscoelastic properties of polyisobutylene melts. *Macromolecules* 24:3136–3141
- Fetters LJ, Kiss AD, Pearson DS, Quack GF, Vitus FJ (1993) Rheological behavior of star-shaped polymers. *Macromolecules* 26:647–654
- Fetters LJ, Lohse DJ, Richter D, Witten TA, Zirkel A (1994) Connection between polymer molecular weight, density, chain dimensions, and melt viscoelastic properties. *Macromolecules* 27:4639–4647
- Fetters LJ, Lohse DJ, Colby R (1996) In: Mark JE (ed) *Chain dimensions and entanglement spacings. Physical properties of polymers*, pp 335–340
- Fetters LJ, Lohse DJ, Graessley WW (1999) Chain dimensions and entanglements spacings in dense macromolecular systems. *J Polym Sci B Polym Phys* 37:1023–1033
- Gell CB, Graessley WW, Letter LJ (1997) Viscoelasticity and self-diffusion in melts of entangled linear polymers. *J Polym Sci B Polym Phys* 35:1933–1942
- Graessley WW, Roovers J (1979) Melt rheology of four-arm and six-arm star polystyrenes. *Macromolecules* 12:959–965
- Graham RS, McLeish TCB, Harlen OG (2001) Using the Pom-Pom equations to analyze polymer melts in exponential shear. *J Rheol* 45:275–290
- Haley JC, Lodge TP, He Y, Ediger MD, von Meerwall ED, Mijovic J (2003) Composition and temperature dependence of terminal and segmental dynamics in polyisoprene/poly(vinylethylene) blends. *Macromolecules* 36:6142–6151
- Keller A, Kolnaar HWH (1997) In: Meijer HEH (ed) *Flow induced orientation and structure formation. Material Science and Technology* 18:189–268
- Kraft M, Meissner J, Kaschta J (1999) Linear viscoelastic characterization of polymer melts with long relaxation times. *Macromolecules* 32:751–757
- Krishnamoorti R, Graessley WW, Zirkel A, Richter D, Hadjichristidis N, Letters LJ, Lohse DJ (2002) Melt-state polymer chain dimensions as a function of temperature. *J Polym Sci B Polym Phys* 40:1768–1776
- Larson RG, Sridhar T, Leal LG, McKinley GH, Likhtman AE, McLeish TCB (2003) Definitions of entanglement spacing and time constants in the tube model. *J Rheol* 47:809–818
- Likhtman AE, McLeish TCB (2002) Quantitative theory for linear dynamics of linear entangled polymers. *Macromolecules* 35:6332–6343
- Majeste JC, Monfort JP, Allan A, Marin G (1998) Viscoelasticity of low molecular weight polymers and the transition to the entangled regime. *Rheol Acta* 37:486–499
- Milner ST, McLeish TCB (1998) Reptation and contour length fluctuations in melts of linear polymers. *Phys Rev Lett* 81:725–728
- Nogales A, Hsiao BS, Somani RHM, Srinivas S, Tsou AH, Balta-Calleja FJ, Eguerra TA (2001) Shear-induced crystallization of isotactic polypropylene with different molecular weight distributions: in situ small- and wide-angle X-ray scattering studies. *Polymer* 42:5247–5256
- Pattamaprom C, Larson RG (2001) Predicting the linear viscoelastic properties of monodisperse and polydisperse polystyrenes and polyethylenes. *Rheol Acta* 40:516–532
- Pattamaprom C, Larson RG, Van Dyke TJ (2000) Quantitative predictions of linear viscoelastic rheological properties of entangled polymers. *Rheol Acta* 39:517–531

- Pearson DS, Ver Strate G, von Meerwall E, Schilling FC (1987) Viscosity and self-diffusion coefficient of linear polyethylene. *Macromolecules* 20:1133–1141
- Pearson DS, Fetters LJ, Younghouse LB, Mays JW (1988) Rheological properties of poly(1,2-dimethyl-1-butenylene) and model atactic polypropylene. *Macromolecules* 21:478–484
- Plazek DL, Plazek DJ (1983) Viscoelastic behavior of atactic polypropylene. *Macromolecules* 16:1469–1475
- Raju VR, Rachpudy H, Graessley WW (1979) Properties of amorphous and crystallizable hydrocarbon polymers. IV. Melt rheology of linear and star-branched hydrogenated polybutadiene. *J Polym Sci Polym Phys Ed* 17:1223–1235
- Raju VR, Menezes EV, Marin G, Graessley WW, Fetters LJ (1981) Concentration and molecular weight dependence of viscoelastic properties of linear and star polymers. *Macromolecules* 14:1668–1676
- Schweizer KS, David EF, Singh C, Curro JG, Rajasekaran JJ (1995) Structure-property correlations of atomistic and coarse-grained models of polymer melts. *Macromolecules* 28:1528–1540
- Seki M, Thurman D, Oberhauser J, Kornfield JA (2002) Shear-mediated crystallization of isotactic polypropylene. The role of long chain-long chain overlap. *Macromolecules* 35:2583–2594
- Struglinski MJ, Graessley WW (1985) Effects of polydispersity on the linear viscoelastic properties of entangled polymers. 1. Experimental observations for binary mixtures of linear polybutadiene. *Macromolecules* 18:2630–2643
- Tsenoglou C (1987) Viscoelasticity of binary homopolymer blends. *ACS Polym Preprints* 28:185–186
- van Meerveld J, Peters GWM, Hütter M (2003) Towards a rheological classification of flow induced crystallization experiments of polymer melts. Preprint
- Vega JF, Aguilar M, Martínez-Salazar J (2003) Model linear metallocene-catalyzed polyolefins: melt rheological behavior and molecular dynamics. *J Rheol* 47:1505–1521
- Vleeshouwers S, Meijer HEH (1996) A rheological study of shear induced crystallization. *Rheol Acta* 35:391–399
- Wasserman SH, Graessley WW (1992) Effects of polydispersity on linear viscoelasticity in entangled polymer melts. *J Rheol* 36:543–572
- Wasserman SH, Graessley WW (1996) Prediction of linear viscoelastic response for entangled polyolefin melts from molecular weight distribution. *Polym Eng Sci* 36:852–861
- Wood-Adams PM, Dealy JM, de Groot AW, Redwine OD (2000) Effect of molecular structure on the linear viscoelastic behavior of polyethylene. *Macromolecules* 33:7489–7499
- Zirkel A, Urban V, Richter D, Fetters LJ, Huang JS, Kampmann R, Hadjichristidis H (1992) Small-angle neutron scattering evaluation of the temperature dependence of atactic polypropylene and poly(1-butene) chain dimensions in the melt. *Macromolecules* 25:6148–6155