

State of the Art and Perspectives in the “Molecular Approach” Towards Well-Defined Heterogeneous Catalysts

Matthew P. Conley · Christophe Copéret

Published online: 4 March 2014
© Springer Science+Business Media New York 2014

Abstract Molecular understanding of heterogeneous catalysts is a key step towards their rational development since catalysis is a molecular phenomenon. Here we describe our efforts towards molecularly defined heterogeneous catalysts through the anchoring of molecular precursors on solid supports and our approaches towards bridging the gap between well-defined and industrial catalysts.

Keywords Catalysis · Molecular approach · Metal oxide · Metal nanoparticle · Grafting

1 Introduction

Catalysis is a key science and technology of the 21st century, and is particularly relevant to develop more efficient, sustainable and cleaner chemical processes. New catalytic processes will have to rely on a wide range of feedstocks, including those derived from biomass, coal and natural gas. Catalysis will also likely be a pillar of the energy domain for fuel cells and conversion of raw materials into liquid fuels. Traditionally catalysis is fragmented between homogeneous, heterogeneous and bio-catalysis, and efforts have been made to bring these disciplines together for many years. A unifying theme between these three fields is the “molecular approach,” because catalysis is a molecular phenomenon where a substrate is converted to intermediates and products on an active site.


While heterogeneous catalysts have been at the heart of chemical processes for more than a century, homogeneous

transition-metal based catalysis has revolutionized the field throughout the last sixty years with the discoveries of many efficient chemical processes, e.g. the highly selective low pressure and low temperature hydroformylation of alkenes, carbonylation of methanol, metallocene polymerization, asymmetric hydrogenation, cross-coupling, olefin/alkyne metathesis and ethylene oligomerization [1]. The molecular understanding of homogeneous catalyst is certainly responsible for the rapid development of highly efficient processes in petro-, bulk and fine chemical syntheses. It is thus not surprising that the catalysis community has recognized this power and tried to implement a “molecular approach” in heterogeneous catalysis [2–5]. Often cited as “Surface Organometallic Chemistry”, this strategy literally constructs molecularly defined active sites at the surfaces of materials [6–11].

Controlling the surface functional group density (e.g. OH for metal oxides like silica or alumina) is the first step in using molecular approaches in heterogeneous catalysis. This control ensures site-isolation between reactive centers and also allows one to tune the chemical environment of a metal complex. The second step involves grafting a molecular transition-metal complex on the reactive surface sites. Generally, an organometallic reagent (L_nM-R) reacts with the surface OH groups in the grafting step to liberate a non-reactive and easily removable alkane byproduct in the grafting step. Molecular precursors containing a displaceable anionic ligand X ($X = Cl, OR, NR_2$, etc.) are also suitable substrates for this reaction (Scheme 1).

The surface species are characterized through establishing the stoichiometry of the reaction and advanced spectroscopic investigation. In some cases computational studies are necessary to gain deeper insight into the molecular structure of the catalyst on the surface by determining the reaction energies and spectroscopic

M. P. Conley · C. Copéret (✉)
Department of Chemistry and Applied Biosciences, ETH Zürich,
Vladimir Prelog Weg 2, 8093 Zürich, Switzerland
e-mail: coperet@ethz.ch

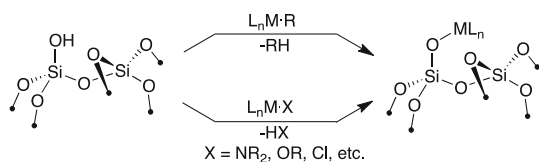

Scheme 1 Grafting organometallic or metalloinorganic complexes on silica

signatures of intermediates. This combination of spectroscopic and theoretical data gives the coordination sphere of the surface complex, including any bonding with surface functionalities. Depending on the application, the surface complex can then be directly used as a well-defined “active site” if the proper ligands have been chosen, ultimately providing a method to draw quantitative structure—activity relationships. The grafted complex can also be used to generate isolated species with controlled surface density through post-treatment steps, or even small metal clusters/nanoparticles depending on the nature of the ligands, the support and the metal [3].


This field has benefited from the development of advanced spectroscopic techniques [12, 13], particularly in the realm of solid-state NMR [14, 15]. Detailed studies of molecular surface equivalents provide precursors, and in some cases mechanistic understanding to complement to spectroscopic characterization data. Computational chemistry has also become a necessary tool in the characterization and design of these molecularly defined heterogeneous catalysts [16].

Here, we will discuss the current state of the art of heterogeneous catalysts using the molecular approach focusing on examples from our research, as well as others closely related works in the field. The goal is not to be exhaustive, but to illustrate recent achievements, directions, and perspectives in the field. We will first describe the simplest systems, reacting organometallic complexes with partially dehydroxylated silica [17], and gradually introduce complexity throughout this perspective before ending with a few examples of studying industrially relevant catalysts using a molecular approach.

2 Well-Defined Metal Complexes Supported on Oxides

2.1 Silica-Supported Catalysts

Silica partially dehydroxylated at 700 °C contains 0.8 OH nm⁻² and large surface areas (200–800 m² g⁻¹). These properties lead to site-isolated silica grafted organometallics that can be characterized by spectroscopic techniques, and for this reason silica is the support of choice to generate isolated metal sites. An illustrative

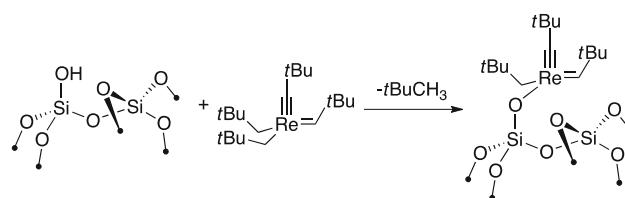


Scheme 2 Grafting an organometallic rhenium alkylidene on silica

example is the development of supported olefin metathesis catalysts, where extensive work has shown that alkylidenes are key reaction intermediates [18, 19]. We synthesized the first well-defined heterogeneous olefin metathesis catalyst based on Re, [(≡SiO)Re(≡CtBu)(=CHtBu)(CH₂tBu)], that was fully characterized by solid state NMR to establish the molecular structure (Scheme 2) [20]. This system showed unprecedented activity in alkene metathesis, even surpassing the best homogeneous catalysts known at the time [21]. The high activity was due to the serendipitous presence of the optimal ligand set: a strong σ -donor alkyl and a weak σ -donor siloxy ligand. This arrangement favors coordination of the incoming olefin *trans*-to the strong σ -donor that in turn destabilizes metallacyclobutane intermediates and favors cycloreversion [22, 23]. With this rule in hand, the isoelectronic silica supported Mo-imido complexes [(≡SiO)Mo(NAr)(=CHR)(Me₂Pyr)] were developed and showed improved stability and activity. [24, 25] It is noteworthy that isostructural MAP catalysts containing similar ligand arrangements (i.e. a strong σ -donor pyrrolide and a weak σ -donor aryloxy) [26–28] are among the best homogeneous catalysts available today. This illustrative example shows the interplay between homogeneous catalysis and heterogeneous catalysis, and the power of the molecular approach [29, 30].

2.2 Alumina-Supported Catalysts

Partially dehydroxylated alumina is a more complex support than silica. At 500 °C alumina contains 2 OH nm⁻², a high density of Lewis acid sites, and a small amount of defect sites (ca. 0.05 nm⁻²). Defect sites have been identified as tricoordinated Al atom facing basic O atoms that result from the presence of chemisorbed H₂O on adjacent aluminums [31]. The tricoordinate aluminum defects coordinate N₂ [32, 33] and readily activate H₂ or CH₄ (Scheme 3) [34]. With early transition metal complexes such as Zr(CH₂tBu)₄, the alumina surface behaves as a bifunctional support, reacting through its OH and its Lewis acid sites to generate supported cationic zirconium-alkyl species, which are highly active towards the polymerization of ethylene [35]. MeReO₃, an organometallic reagent insensitive to protic media, reacts with alumina defects by C–H activation of the methyl group

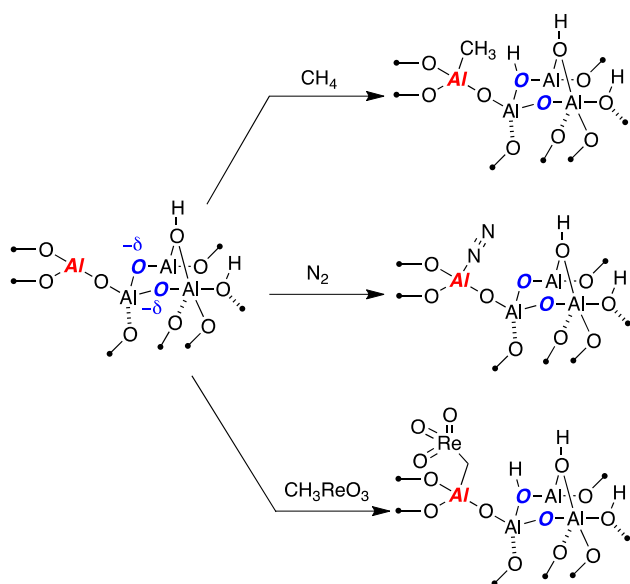


Scheme 3 C-H activation of methane and CH_3ReO_3 on Al_2O_3 defect sites

to generate a μ^2 -methylene species, which are highly active in alkene metathesis [36, 37].

2.3 Stabilization of Highly Reactive Species

Surface species are typically more stable than their homogeneous equivalents and can lead to unprecedented reactivities. It has been shown in alkene metathesis by comparing the catalytic performances of isoelectronic and isostructural molecular and surface complexes [38]. The surface supported species $[(\equiv\text{SiO})\text{Mo}(\text{NAr})(=\text{CHtBu})(\text{CH}_2\text{tBu})_2]$ is more reactive and stable than the homogeneous equivalent because site-isolation shuts down bimolecular decomposition pathways. Another similar example is the reaction of $[(\equiv\text{SiO})\text{Ta}(\text{=CHtBu})(\text{CH}_2\text{tBu})_2]$ with propane at 150 °C, which gives RCH_2tBu ($\text{R} = \text{H}, \text{Me}, \text{Et}$) along with metathesis products (ethane and butane) [39, 40]. Surface species of early transition-metals can also be converted to highly

Scheme 4 Formation of zirconium hydrides on silica

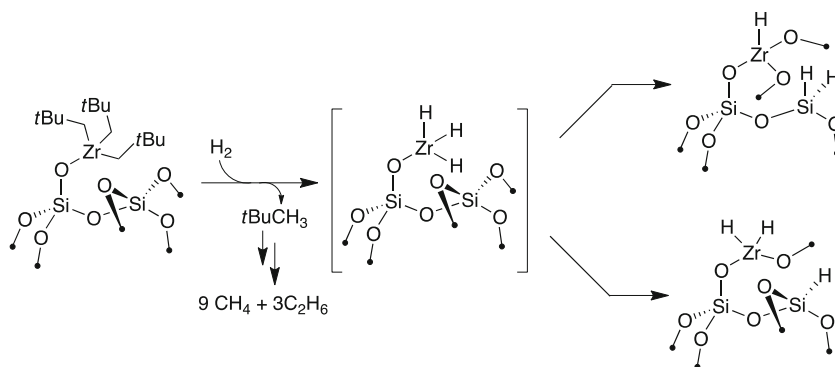


electron deficient or coordinatively unsaturated metal-hydrides, such as $[(\equiv\text{SiO})_{4-x}\text{ZrH}_x]$ ($x = 1$ or 2, Scheme 4) or $(\equiv\text{SiO})_2\text{TaH}_y$ ($y = 1$ or 3), due to the formation of additional M–O bonds by subsequent reactions of the grafted metal complex with adjacent siloxane bridges [3, 41]. These species catalyze the low temperature hydrogenolysis of alkanes [42, 43], the metathesis of alkanes [44–47], the cross-metathesis of methane and propane [48] and the non-oxidative coupling of methane at relatively low temperatures [49].

3 Supported Homogeneous Catalysts Through the Controlled Functionalization of Hybrid Materials

In view of the plethora of ligands in homogeneous catalysis, another effort has been directed at synthesizing so-called supported homogeneous catalysts. In these catalysts the organic ligand is attached to the surface of a material, typically an oxide like silica since it develops a large surface area. Typically in this area an organosilane precursor is contacted with a silica material to anchor the organic functionality to the surface of a material (Scheme 5a) [50, 51]. Though effective in some cases, this approach does not control the distribution of ligands or the number of bonds between the organic residue and the surface. Recent developments in material chemistry have found solutions to this problem by imbedding the organic ligand in the silica matrix at the synthesis stage in the presence of a surfactant [52, 53]. The surfactant leads not only to a structuration of the material (e.g. 2D hexagonal) [54], but also to the controlled incorporation and distribution of the organic fragment along the pore channel (Scheme 5b). The homogeneous distribution of the ligands with the silica matrix has been recently validated by EPR spectroscopy [55].

While this approach has been exploited very early in acid–base catalysis [56–59], it has only been recently applied to transition-metal complexes. In the latter case, it is necessary to avoid the reaction of the metal with the

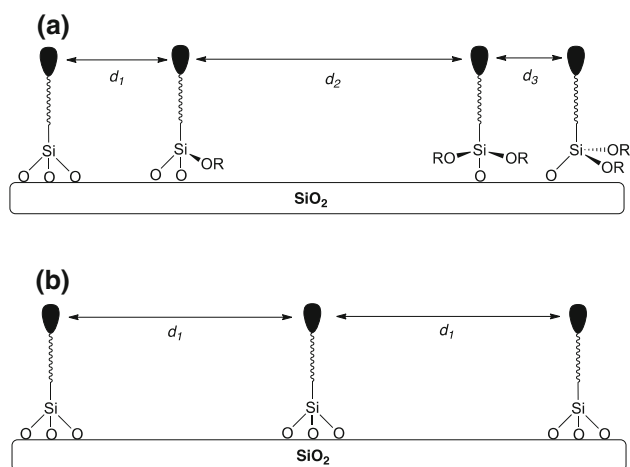


Scheme 5 **a** Surface species generated from grafting alkoxy-silanes on silica; **b** Surface species from surfactant mediated material synthesis

oxide surface and to insure that the metal is strongly bound to a stable ligand. Passivation of the surface with trimethylsilyl groups overcomes the first challenge. *N*-heterocyclic carbenes (NHC) were the first successful results with application with a wide range of catalytic reactions: H/D exchange of unactivated C–H bonds [60], alkene metathesis [61, 62], CO₂ hydrogenation [63], and the semi-hydrogenation of alkynes (Scheme 6) [64].


The tether can have a great influence on the catalytic performance of a surface tethered catalyst (Scheme 7). For instance, the Ru-NHC metathesis catalyst having a flexible propyl linker shown in Scheme 7 yields a catalyst without phosphine ligand, though surprisingly stable stability; in contrast to the rigid phenylmesityl equivalent. These results point to the beneficial role of the surface: the flexible linker allows interactions with the surface, as shown by DNP SENS, and stabilizes of the surface Ru-species [62].

4 Controlling the Composition, the Growth and the Interface of Supported Metal Particles

One of the important advantages of using organometallic precursors in place of metal salts as nanoparticles sources avoids unwanted halogen contaminants or adventitious salt residues. In fact, organometallics dispersed on a support readily decompose under mild conditions with only H₂ as reducing agent to afford metal nanoparticles [65]. For instance, small (<2 nm) and narrowly dispersed Ru and Os nanoparticles can be obtained by decomposition of silica wetted with Ru(cod)(cot) and Os(cod)(cot) under H₂ [66, 67]. Particle size and density is also controllable by grafting a molecular precursor prior to its decomposition under H₂ [68–70]. Finally, by choosing specific molecular precursors, it is

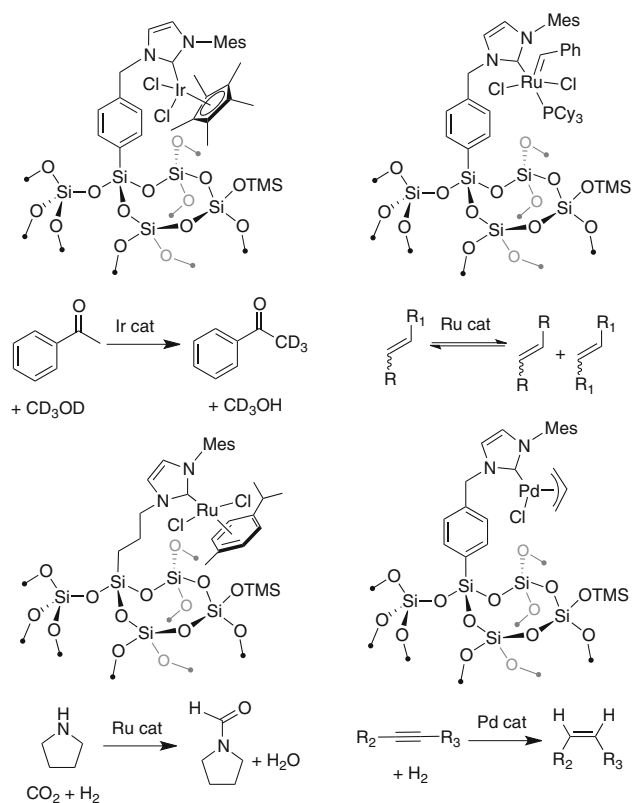


Scheme 6 Functionalized NHC-M complexes in hybrid materials

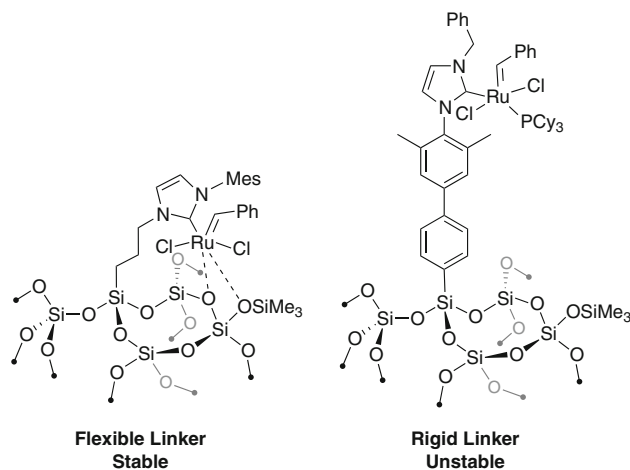

Scheme 7 Linker flexibility determines metal-surface interaction and stability for NHC-Ru metathesis catalysts

even possible to generate supported metallic nanoparticles while controlling the solid-particle interface. For instance, grafting of [Au(N(SiMe₃)₂)₄] and subsequent treatment under H₂ (Scheme 8) generates 1.8 nm gold nanoparticles supported on a passivated silica lacking OH groups, which greatly improved the performances in the aerobic epoxidation of stilbene [71].

Scheme 8 Formation of Au nanoparticles after grafting an metalloinorganic complex

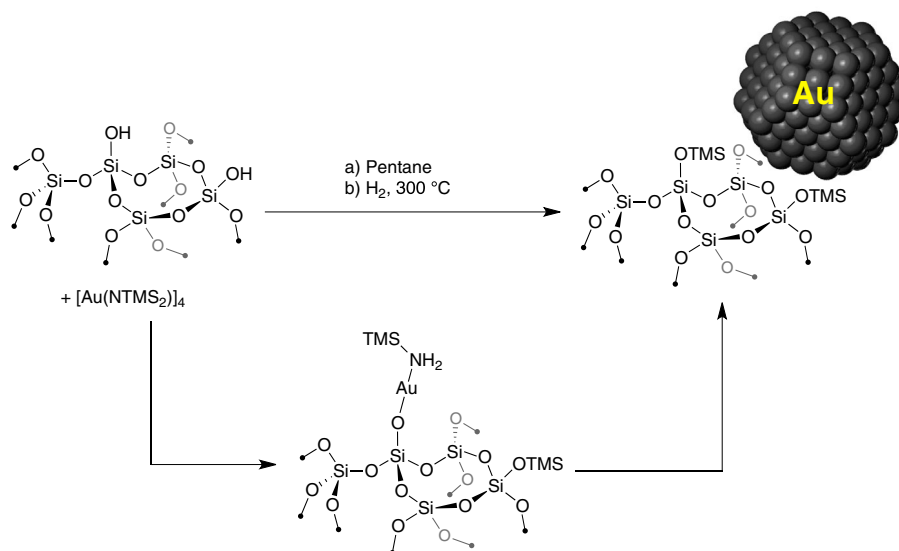

5 Advances in Characterization Tools: Dynamic Nuclear Polarization–Surface Enhanced NMR Spectroscopy (DNP–SENS)

The molecular approach requires detailed characterization of surface species, which typically constitutes a very small fraction of the sample (<1–5 % in most cases). While NMR is the most powerful technique to assess structure of at a molecular level, particularly for molecules supported on amorphous supports, this method is inherently insensitive. As a consequence tedious labeling of the sample is often required in order to obtain NMR spectra in reasonable times (<24 h). Following the pioneering work of R. Griffin [72, 73], we have recently developed a technique coined DNP–SENS, Dynamic Nuclear Polarization Surface Enhanced NMR spectroscopy, that allows the selective NMR signal enhancement of surface species [74, 75]. This technique requires impregnation of a material with a minimum amount of a nitroxyl diradical solution (10–20 mM) and loading the sample into a pre-cooled (100 K) solid-state NMR spectrometer equipped with a high power single frequency microwave gyrotron, currently commercially available from Bruker. The microwave irradiation at low temperature results in the efficient polarization transfer of the electrons to protons, and CP-MAS from the protons to the desired nuclei results in signal enhancement (carbon-13, nitrogen-15 [76], silicon-29 [75], aluminium-27 [77]). The NMR signals can theoretically be enhanced by a factor of 660 ($\gamma_e/\gamma_H = 660$) corresponding to a decrease in acquisition time by ca. 440,000. In other words, an experiment that would take place in 300 days without SENS would take 1 min with a signal enhancement of 660.

Our first experiments were performed with TOTAPOL [78] as the polarizing agent in water. We have shown that

organic solvents such as toluene or tetrachloroethane work very well and give large enhancements with the family of bTbk radicals, ranging from 20 to 50 for parent bTbk [32] to more than 200 for TEKPol [79]. Originally discovered with simple hybrid organic–inorganic materials, this technique has been applied to alumina [77, 80], zeolites [81], and more recently to characterize well-defined metal complexes bound to the surface of hybrid materials [64, 82] (Scheme 9).


6 Bridging the Gap between Well-Defined Species and Classical Heterogeneous Catalysts

Industry relies extensively on supported catalysts for the production of polymers. This can be found in the Philipps and Ziegler–Natta olefin polymerization catalysts, which provide range of materials used in everyday life. While catalysis very likely takes place at a single-metal center, the aforementioned catalysts are in fact quite complex, and the structure of their active sites are not known, though Surface Organometallic Chemistry has provided some information concerning the interaction of metallocene complexes with oxide surfaces [83–87].

The classical Ziegler–Natta catalysts, $[TiCl_4.MgCl_2.L]$, where $L = EtOH, THF$, or other alcohols/ethers, have been studied in detail by X-ray Absorption Spectroscopy [88, 89]. NMR spectroscopy combined with computational modeling has revealed that the THF ligand in $[TiCl_4.MgCl_2.THf]$ is not innocent, and generates an alkoxy surface species as the result of its ring opening (Scheme 10a) [90]. While similar alkoxy species are formed with other L such as ethanol, it is not clear what the importance/relevance of such surface species to the final catalytic active sites.

In the case of Phillips catalyst, silica-supported Cr oxide species, the ideal oxidation state of the active species and

Scheme 9 a–d Nitroxyl radicals used for SENS; **e** SENS spectrum of a hybrid-silica material containing phenol groups in the mesopores with microwaves on (*top spectrum*) and microwaves off (*bottom spectrum*)

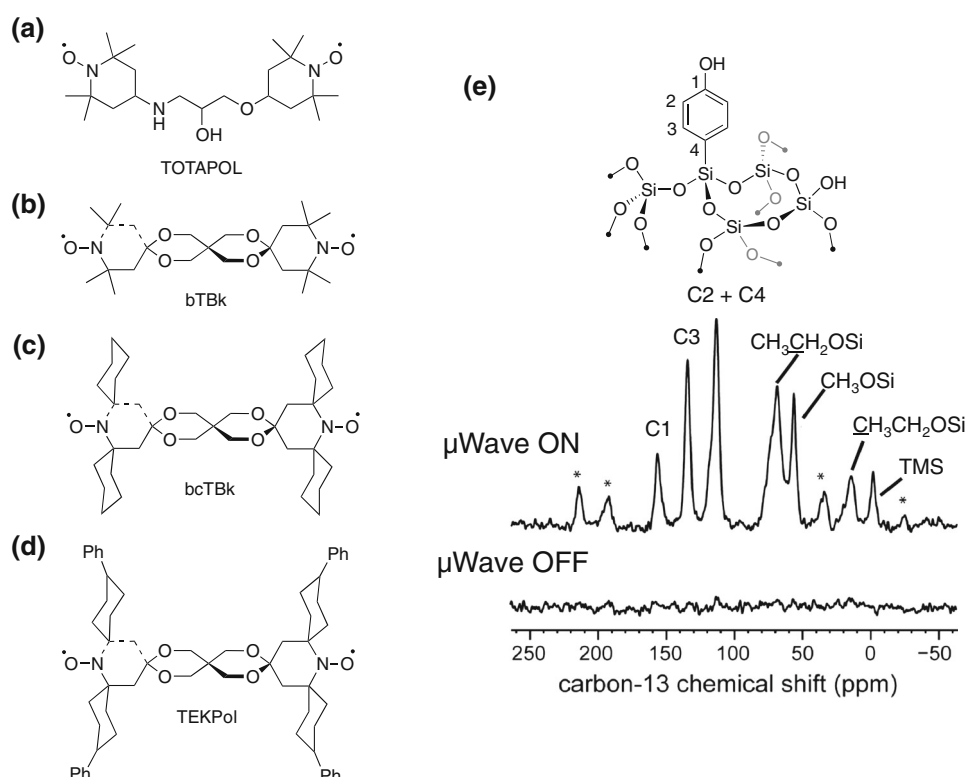

the formation of the first Cr–C bond remain controversial [91–94]. Recent efforts from our laboratory have shown that dinuclear Cr(III) silicates are highly active in ethylene polymerization while the Cr(II) analogues are much less active, suggesting that Cr(III) is probably the active polymerization oxidation state (Scheme 10b). Notably, similar observations have been made for homogeneous chromium polymerization catalysis [95, 96]. In addition, we have shown that the formation of the active species results from the heterolytic C–H activation of ethylene on a Cr–O bonds, which opens a new paradigm in polymerization catalysis and may shed light on the initiation mechanism of the classical Phillips catalyst [97].

Another well-know “single-site” industrial catalyst is the silica supported TiCl_4 propene epoxidation catalyst [98]. Combining a detailed reaction analysis, advanced NMR spectroscopy, and computational chemistry has revealed that the primary $\equiv \text{SiOTiCl}_3$ surface species readily reorganizes upon thermal treatment at high temperature by reaction with adjacent siloxane bridges and adjacent $\equiv \text{SiOTiCl}_3$ to generate stable $(\equiv \text{SiO})_2\text{TiCl}_2$ and TiCl_4 (Scheme 10c) [99].

With the advancement of spectroscopic techniques and computational chemistry, it is now possible to study complex systems, even the aforementioned industrial catalysts, to provide new molecular views on existing systems.


7 Conclusions and Perspectives

With our current level of understanding of the surface chemistry of oxides, in particular silica and alumina, we can predictively design and prepare highly active and selective supported catalysts with molecular level definition. Molecular approaches can also help to directly address structure–activity relationships in industrial catalysts, with the goal of addressing one of the major challenges in industrial catalysis: developing more robust/stable catalysts.

The ‘simple’ grafting strategy is one step closer to using surfaces in a similar way ligands are used in homogeneous catalysis. Not discussed here are the opportunities on other supports. For example, mixed metal oxides have benefited from molecular approaches in non-hydrolytic sol–gel of mixed metal oxides [100] and the thermolysis of molecular precursors [101]. Though these methods have already shown interesting features, in particular the control of material composition and the discrete arrangement of atoms within mixed metal oxides, very little has been done in understanding the structures and the reactivities of these surfaces.

Hybrid organic–inorganic materials, silica-based materials with pendant ligand in the pores, offer intriguing material compositions that can directly functionalized as catalysts. Similar to this approach, a large effort is currently focusing on metal organic frameworks and related materials as a source of well-defined chemical environments for

Scheme 10 Transferring the molecular approach to industrial heterogeneous catalysts

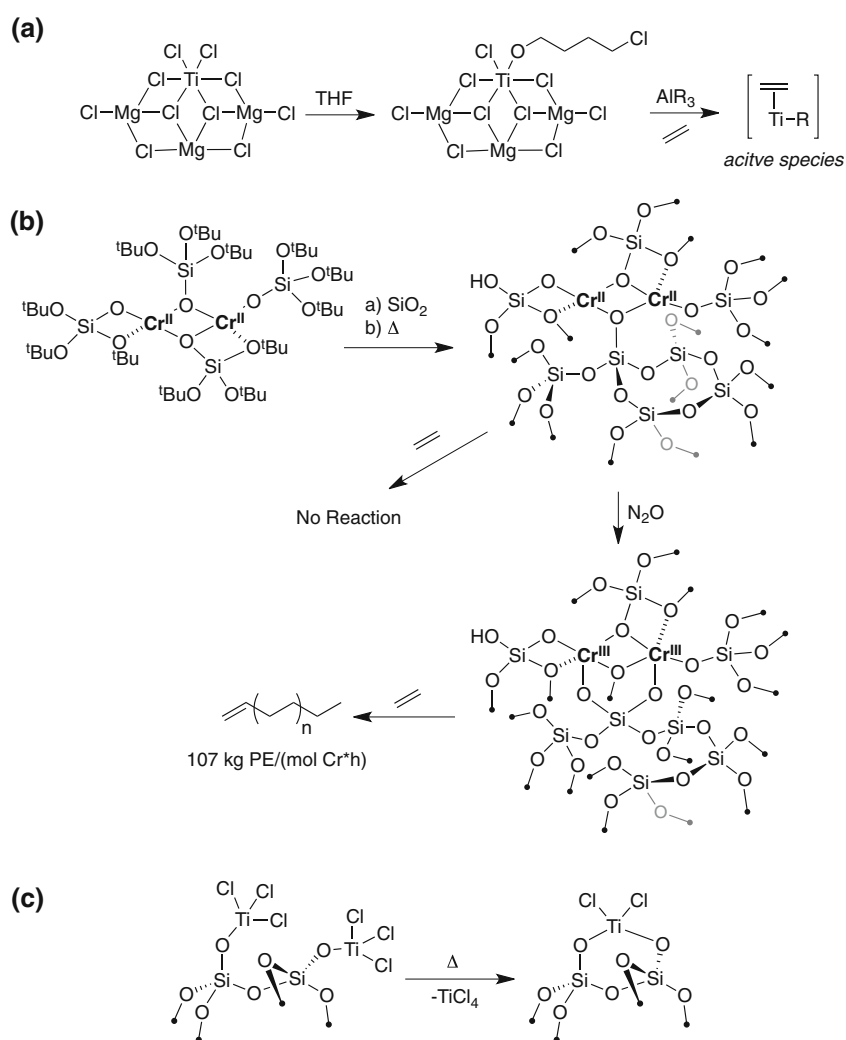

catalysis [102]. The realm of silica-based materials is not only limited to SBA type structures. In particular periodic mesoporous silicates are a promising platform of materials that have high levels of structural order, good thermal stability, and large pore volume [103, 104].

The above materials are considered as model supports and catalysts. One of the largest classes of industrially relevant catalysts is supported nanoparticles for which a clear need for more molecular level investigations persists. The use of well-defined molecular precursors has already shown some promise with the control of size and distribution of particles as well as the interface between the metallic nanoparticles and the support. However, the need to reach smaller nanoparticles with a narrower particle size distribution has recently led to colloidal approaches [105–107]. Combining material chemistry of oxide and colloidal chemistry can also open new opportunities [108]. Material chemistry has shown the possibility to control the shape and the texture of oxide materials, and to incorporate metal nanoparticles within the pore or the wall of the material

[109, 110]. This could provide several advantages, such as reducing the possibility for sintering or the preparation of bifunctional systems.

Molecular approaches, whether discussing surface science or surface chemistry, is clearly an essential tool in rational design. The molecular approach will continue to blossom as the advances in spectroscopy, material and molecular chemistry continue, and will likely be key to the development of optimal catalysts.

References

1. van Leeuwen PWNM, Chadwick JC (2011) Homogeneous Catalysts Activity—Stability—Deactivation. Wiley-VCH, Weinheim
2. Ballard DGH (1973) Adv Catal 23:263
3. Yermakov YI (1981) Stud Surf Sci Catal 7:57
4. Burwell RL (1984) J Catal 86:301
5. Surface Organometallic Chemistry: Molecular Approaches to Surface Catalysis, 231 (1988). NATO Advanced Science Institutes Series, Series C; Mathematical and Physical Sciences

6. Copéret C, Chabanas M, Petroff Saint-Arroman R, Basset JM (2003) *Angew Chem Int Ed* 42:156
7. Wegener SL, Marks TJ, Stair PC (2011) *Acc Chem Res* 45:206
8. Thomas JM, Raja R, Lewis DW (2005) *Angew Chem Int Ed* 44:6456
9. Tada M, Iwasawa Y (2007) *Coord Chem Rev* 251:2702
10. Liang Y, Anwender R (2013) *Dalton Trans* 42:12521
11. Guzman J, Gates BC (2003) *Dalton Trans* 17:3303
12. Beale AM, Weckhuysen BM (2010) *Phys Chem Chem Phys* 12:5562
13. Lesage A (2010) *Phys Chem Chem Phys* 12:5502
14. Blanc F, Copéret C, Lesage A, Emsley L (2008) *Chem Soc Rev* 37:518
15. Conley MP, Copéret C (2012) *Chimia* 66:752
16. Sautet P, Delbecq F (2010) *Chem Rev* 110:1788
17. Rascon F, Wischert R, Copéret C (2010) *Chem Sci* 2:1449
18. Schrock RR (2006) *Angew Chem Int Ed* 45:3748
19. Grubbs RH (2006) *Angew Chem Int Ed* 45:3760
20. Chabanas M, Baudouin A, Copéret C, Basset J-M (2001) *J Am Chem Soc* 123:2062
21. Chabanas M, Copéret C, Basset J-M (2001) *Chem Eur J* 9:971
22. Solans-Monfort X, Clot E, Copéret C, Eisenstein O (2005) *J Am Chem Soc* 127:14015
23. Poater A, Solans-Monfort X, Clot E, Copéret C, Eisenstein O (2007) *J Am Chem Soc* 129:8207
24. Blanc F, Berthoud R, Salameh A, Basset J-M, Copéret C, Singh R, Schrock RR (2007) *J Am Chem Soc* 129:8434
25. Copéret C (2007) *Dalton Trans* 47:5498
26. Jiang AJ, Simpson JH, Mueller P, Schrock RR (2009) *J Am Chem Soc* 131:7770
27. Jiang AJ, Zhao Y, Schrock RR, Hoveyda AH (2009) *J Am Chem Soc* 131:16630
28. Marinescu SC, Schrock RR, Mueller P, Hoveyda AH (2009) *J Am Chem Soc* 131:10840
29. Malcolmson SJ, Meek SJ, Sattely ES, Schrock RR, Hoveyda AH (2008) *Nature* 456:933
30. Hoveyda AH, Zhugralin AR (2007) *Nature* 450:243
31. Wischert R, Laurent P, Copéret C, Delbecq F, Sautet P (2012) *J Am Chem Soc* 134:14430
32. Zagdoun A, Rossini AJ, Gajan D, Bourdolle A, Ouari O, Rosay M, Maas WE, Tordo P, Lelli M, Emsley L, Lesage A, Copéret C (2012) *Chem Comm* 48:654
33. Wischert R, Copéret C, Delbecq F, Sautet P (2011) *Chem Comm* 47:4890
34. Wischert R, Copéret C, Delbecq F, Sautet P (2011) *Angew Chem Int Ed* 50:3202
35. Joubert J, Delbecq F, Sautet P, Roux EL, Taoufik M, Thieuleux C, Blanc F, Copéret C, Thivolle-Cazat J, Basset J-M (2006) *J Am Chem Soc* 128:9157
36. Salameh A, Joubert J, Baudouin A, Lukens W, Delbecq F, Sautet P, Basset J-M, Copéret C (2007) *Angew Chem Int Ed* 46:3870
37. Salameh A, Baudouin A, Soulivong D, Boehm V, Roeper M, Basset J-M, Copéret C (2008) *J Catal* 253:180
38. Blanc F, Copéret C, Thivolle-Cazat J, Basset J-M, Lesage A, Emsley L, Sinha A, Schrock RR (2006) *Angew Chem Int Ed* 45:1216
39. Copéret C, Maury O, Thivolle-Cazat J, Basset J-M (2001) *Angew Chem Int Ed* 40:2331
40. Blanc F, Thivolle-Cazat J, Basset J-M, Copéret C (2008) *Chem Eur J* 14:9030
41. Vidal V, Théolier A, Thivolle-Cazat J, Basset J-M, Corker J (1996) *J Am Chem Soc* 118:4595
42. Chabanas M, Vidal V, Copéret C, Thivolle-Cazat J, Basset J-M (2000) *Angew Chem Int Ed* 39:1962
43. Lecuyer C, Quignard F, Choplin A, Olivier D, Basset J-M (1991) *Angew Chem Int Ed* 30:1660
44. Vidal V, Théolier A, Thivolle-Cazat J, Basset J-M (1997) *Science* 276:99
45. Thieuleux C, Maraval A, Veyre L, Copéret C, Soulivong D, Basset J-M, Sunley GJ (2007) *Angew Chem Int Ed* 46:2288
46. Basset J-M, Copéret C, Soulivong D, Taoufik M, Thivolle-Cazat J (2010) *Acc Chem Res* 43:323
47. Copéret C (2010) *Chem Rev* 110:656
48. Soulivong D, Copéret C, Thivolle-Cazat J, Basset J-M, Maunders BM, Pardy RBA, Sunley GJ (2004) *Angew Chem Int Ed* 43:5366
49. Soulivong D, Norsic S, Taoufik M, Copéret C, Thivolle-Cazat J, Chakka S, Basset J-M (2008) *J Am Chem Soc* 130:5044
50. Diaz U, Brunel D, Corma A (2013) *Chem Soc Rev* 42:4083
51. Brunel D, Bellocq N, Sutra P, Cauvel A, Lasperas M, Moreau P, Di Renzo F, Galarneau A, Fajula F (1998) *Coord Chem Rev* 178:1085
52. Hoffmann F, Cornelius M, Morell J, Fröba M (2006) *Angew Chem Int Ed* 45:3216
53. Corriu RJP, Mehdi A, Reye C (2005) *J Mater Chem* 15:4285
54. Zhao D, Feng J, Huo Q, Melosh N, Fredrickson GH, Chmelka BF, Stucky GD (1998) *Science* 279:548
55. Gajan D, Schwarzwälder M, Conley MP, Gruening WR, Rossini AJ, Zagdoun A, Lelli M, Yulikov M, Jeschke G, Sauvée C, Ouari O, Tordo P, Veyre L, Lesage A, Thieuleux C, Emsley L, Copéret C (2013) *J Am Chem Soc* 135(41):15459–15466. doi:10.1021/ja405822h
56. Margelefsky EL, Zeidan RK, Davis ME (2008) *Chem Soc Rev* 37:1118
57. Bass JD, Anderson SL, Katz A (2003) *Angew Chem Int Ed* 42:5219
58. Gonzalez-Arellano C, Corma A, Iglesias M, Sanchez F (2005) *Chem Comm* 27:3451
59. Brunelli NA, Venkatasubbaiah K, Jones CW (2012) *Chem Mater* 24:2433
60. Maishal TK, Alauzun J, Basset J-M, Copéret C, Corriu RJP, Jeanneau E, Mehdi A, Reyé C, Veyre L, Thieuleux C (2008) *Angew Chem Int Ed* 47:8654
61. Karamé I, Boualleg M, Camus J-M, Maishal TK, Alauzun J, Basset J-M, Copéret C, Corriu RJP, Jeanneau E, Mehdi A, Reyé C, Veyre L, Thieuleux C (2009) *Chem Eur J* 15:11820
62. Samantaray MK, Alauzun J, Gajan D, Kavitate S, Mehdi A, Veyre L, Lelli M, Lesage A, Emsley L, Copéret C, Thieuleux C (2013) *J Am Chem Soc* 135:3193
63. Baffert M, Maishal TK, Mathey L, Copéret C, Thieuleux C (2011) *Chem Sus Chem* 4:1762
64. Conley MP, Drost RM, Baffert M, Gajan D, Elsevier C, Franks WT, Oschkinat H, Veyre L, Zagdoun A, Rossini AJ, Lelli M, Lesage A, Casano G, Ouari O, Tordo P, Emsley L, Copéret C, Thieuleux C (2013) *Chem Eur J* 19:12234
65. Kahn ML, Glaria A, Pages C, Monge M, Saint Macary L, Maisonnat A, Chaudret B (2009) *J Mater Chem* 19:4044
66. Berthoud R, Délichère P, Gajan D, Lukens W, Pelzer K, Basset J-M, Candy J-P, Copéret C (2008) *J Catal* 260:387
67. Low JE, Foelske-Schmitz A, Krumeich F, Worle M, Baudouin D, Rascon F, Copéret C (2013) *Dalton Trans* 42:12620
68. Laurent P, Veyre L, Thieuleux C, Donet S, Copéret C (2013) *Dalton Trans* 42:238
69. Choi YS, Moschetta EG, Miller JT, Fasulo M, McMurdo MJ, Rioux RM, Tilley TD (2011) *ACS Catal* 1:1166
70. Bonati MLM, Douglas TM, Gaemers S, Guo N (2012) *Organometallics* 31:5243
71. Gajan D, Guillois K, Delichère P, Basset J-M, Candy J-P, Caps V, Copéret C, Lesage A, Emsley L (2009) *J Am Chem Soc* 131:14667
72. Becerra LR, Gerfen GJ, Temkin RJ, Singel DJ, Griffin RG (1993) *Phys Rev Lett* 71:3561

73. Rosay M, Tometich L, Pawsey S, Bader R, Schauwecker R, Blank M, Borchard PM, Cauffman SR, Felch KL, Weber RT, Temkin RJ, Griffin RG, Maas WE (2010) *Phys Chem Chem Phys* 12:5850
74. Lesage A, Lelli M, Gajan D, Caporini MA, Vitzthum V, Miéville P, Alauzun J, Roussey A, Thieuleux C, Mehdi A, Bodenhausen G, Copéret C, Emsley L (2010) *J Am Chem Soc* 132:15459
75. Lelli M, Gajan D, Lesage A, Caporini MA, Vitzthum V, Miéville P, Héroguel F, Rascon F, Roussey A, Thieuleux C, Boualleg M, Veyre L, Bodenhausen G, Copéret C, Emsley L (2011) *J Am Chem Soc* 133:2104
76. Zagdoun A, Casano G, Ouari O, Lapadula G, Rossini AJ, Lelli M, Baffert M, Gajan D, Veyre L, Maas WE, Rosay M, Weber RT, Thieuleux C, Copéret C, Lesage A, Tordo P, Emsley L (2011) *J Am Chem Soc* 134:2284
77. Vitzthum V, Mieville P, Carnevale D, Caporini MA, Gajan D, Copéret C, Lelli M, Zagdoun A, Rossini AJ, Lesage A, Emsley L, Bodenhausen G (2012) *Chem Comm* 48:1988
78. Song C, Hu KN, Joo CG, Swager TM, Griffin RG (2006) *J Am Chem Soc* 128:11385
79. Zagdoun A, Casano G, Ouari O, Schwarzwälder M, Rossini AJ, Aussenac F, Yulikov M, Jeschke G, Copéret C, Lesage A, Tordo P, Emsley L (2013) *J Am Chem Soc* 135(34):12790–12797. doi:10.1021/ja405813t
80. Lee D, Takahashi H, Thankamony ASL, Dacquin J-P, Bardet M, Lafon O, Paepe G (2012) *J Am Chem Soc* 134:18491
81. Lafon O, Rosay M, Aussenac F, Lu X, Trébosc J, Cristini O, Kinowski C, Touati N, Vezin H, Amoureux J-P (2011) *Angew Chem Int Ed* 50:8367
82. Gruning WR, Rossini AJ, Zagdoun A, Gajan D, Lesage A, Emsley L, Copéret C (2013) *Phys Chem Chem Phys* 15:13270
83. Jezequel M, Dufaud V, Ruiz-Garcia MJ, Carrillo-Hermosilla F, Neugebauer U, Niccolai GP, Lefebvre F, Bayard F, Corker J, Fiddy S, Evans J, Broyer J-P, Malinge J, Basset J-M (2001) *J Am Chem Soc* 123:3520
84. Millot N, Soignier S, Santini CC, Baudouin A, Basset J-M (2006) *J Am Chem Soc* 128:9361
85. Kim SH, Somorjai GA (2006) *Proc Nat Acad Sci* 103:15289
86. Kaminsky W, Poly J (2004) *Sci A* 42:3911
87. Williams LA, Marks TJ (2011) *ACS Catal* 1:238
88. Seenivasan K, Gallo E, Piovano A, Vitillo JG, Sommazzi A, Bordiga S, Lamberti C, Glatzel P, Groppo E (2013) *Dalton Trans* 42:12706
89. Gallo E, Lamberti C, Glatzel P (2011) *Phys Chem Chem Phys* 13:19409
90. Grau E, Lesage A, Norsic S, Copéret C, Monteil V, Sautet P (2012) *ACS Catal* 3:52
91. McDaniel MP (2010) *Adv Catal* 53:123
92. Groppo E, Estephane J, Lamberti C, Spoto G, Zecchina A (2007) *Catal Today* 126:228
93. Groppo E, Lamberti C, Bordiga S, Spoto G, Zecchina A (2005) *Chem Rev* 105:115
94. Bordiga S, Groppo E, Agostini G, van Bokhoven JA, Lamberti C (2013) *Chem Rev* 113:1736
95. Theopold KH (1998) *Eur J Inorg Chem* 1:15
96. MacAdams LA, Buffone GP, Incarvito CD, Rheingold AL, Theopold KH (2005) *J Am Chem Soc* 127:1082
97. Conley MP, Delley MF, Siddiqi G, Lapadula G, Norsic S, Monteil V, Safonova OV, Copéret C (2014) *Angew Chem Int Ed Engl* 53(7):1872–1876
98. Cavani F, Teles JH (2009) *Chem Sus Chem* 2:508
99. Mania P, Verel R, Jenny F, Hammond C, Hermans I (2013) *Chem Eur J* 19:9849
100. Mutin PH, Vioux A (2009) *Chem Mater* 21:582
101. Furdala KL, Tilley TD (2003) *J Catal* 216:265
102. Wang C, Liu D, Lin W (2013) *J Am Chem Soc* 135(36):13222–13234. doi:10.1021/ja308229p
103. Waki M, Mizoshita N, Tani T, Inagaki S (2011) *Angew Chem Int Ed* 50:11667
104. Inagaki S, Guan S, Ohsuna T, Terasaki O (2002) *Nature* 416:304
105. An K, Somorjai GA (2012) *Chem Cat Chem* 4:1512
106. Cormary B, Dumestre F, Liakakos N, Soulantica K, Chaudret B (2013) *Dalton Trans* 42:12546
107. Corma A, Garcia H (2008) *Chem Soc Rev* 37:2096
108. Baudouin D, Szeto KC, Laurent P, De Mallmann A, Fenet B, Veyre L, Rodemerck U, Copéret C, Thieuleux C (2012) *J Am Chem Soc* 134:20624
109. Boualleg M, Norsic S, Baudouin D, Sayah R, Quadrelli EA, Basset J-M, Candy JP, Delichere P, Pelzer K, Veyre L, Thieuleux C (2011) *J Catal* 284:184
110. Arnal PM, Comotti M, Schuth F (2012) *Angew Chem Int Ed* 45:8224